

Product description

Colour	Weight (mg)	Size (mm)	Bulk density (g/l)	Packaging	Approved for direct food contact
Black	1.0	2.0 – 3.5	49.0 – 57.0	Bulk	No

Physical properties

	Test method	20g/l	30g/l	40g/l	50g/l	60g/l	70g/l
Compressive strength							
25% strain (kPa)	ISO 844	80	150	210	275	340	425
50% strain (kPa)	5mm/min	150	220	300	370	475	580
75% strain (kPa)		370	460	600	800	1,000	1,250
Compression set							
25% strain – 22 hours – 23°C (%)	ISO 1856 (Method C) Stabilising 24h	12.5	12.0	11.5	11.5	11.5	11.0
Burn rate (mm/min)							
	ISO 3795 12.5mm thick	115	80	60	50	40	35


ARPRO 5253 RE is for on-site expansion between 16g/l and 42g/l.



ARPRO 5253 RE contains 25% recycled end-of-life moulded parts. Its production contributes to reduce CO₂ emissions by 11% compared to ARPRO Black!

Moulding

ARPRO 5253 RE requires on-site expansion prior to moulding. The table below illustrates the bulk density range achievable through on-site expansion and the respective moulding process required to then achieve the target moulded density. For direct moulding of 5253 RE without expansion, please contact the ARPRO technical team for support.

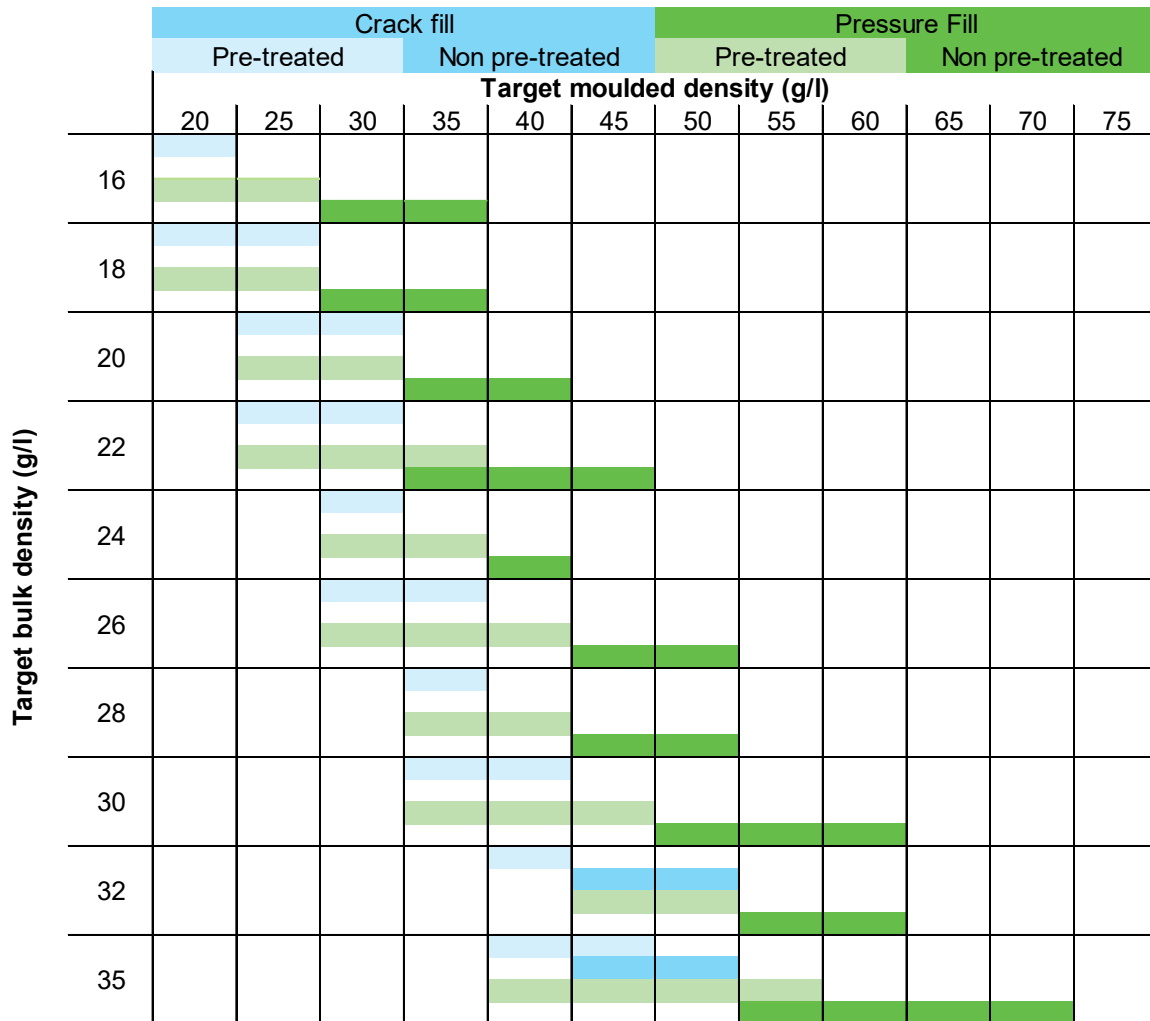

Pre-treatment

Pre-treatment recommendations are available in the respective ARPRO black grade sheets at ARPRO.com.

Post-treatment

For moulded densities below 50g/l and depending on the parts dimensions, post-treatment at a temperature of 80°C is recommended for 3 to 8 hours. This helps to remove water content, as well as ensuring dimensional stability and a geometric shape.

For moulded densities above 50g/l, post-treatment is not required. Stabilisation to ambient conditions for 4 hours before dimensional quality testing is recommended.

Shrinkage

Typical values range from 1.8% to 3.5%. The higher the moulded density, typically the lower the shrinkage.

Storage

A storage temperature above 15°C is strongly recommended.

Indoor storage strongly recommended.

If stored outdoors, it is strongly recommended to keep the material indoors for 24 hours before moulding.

Version 04

This information is provided as a convenience to customers and reflects the results of internal tests conducted on ARPRO samples. While all reasonable care has been taken to ensure that this information is accurate as of the date of issue, JSP does not represent, warrant or otherwise guarantee, expressly or impliedly, the suitability, accuracy, reliability or completeness of the information. ARPRO is a registered trade mark.