

## Product description

Colour	Weight (mg)	Size (mm)	Bulk density (g/l)	Packaging	Food approved
Grey	1.5	2.0 - 6.0	23.0 - 27.0	Bulk / Bag	Yes

## Physical properties

	Test method	30g/l	40g/l
Compressive strength 25% strain (kPa) 50% strain (kPa) 75% strain (kPa)	ISO 844 5mm/min	140 220 465	190 285 600
Compression set 25% strain – 22 hours – 23°C (%)	ISO 1856 C Stabilising 24h	8.0	8.0
Burn rate (mm/min)	ISO 3795 12.5mm thick	65	50
Acoustic absorption coefficient	ISO 354 1,250Hz 30mm	0.62	0.67


ARPRO 4025 has a porosity that absorbs sound from 400 to 10,000Hz and allows water and liquids of similar viscosity to pass through.

## Moulding

ARPRO 4025 can be moulded using Crack Fill (CF) and Pressure Fill (PF):

Crack fill: applied to either Pre-Treated (PT) or Non-Pre-Treated (NPT) ARPRO.


Pressure fill: applied to either Pre-Treated (PT) or Non-Pre-Treated (NPT) ARPRO.

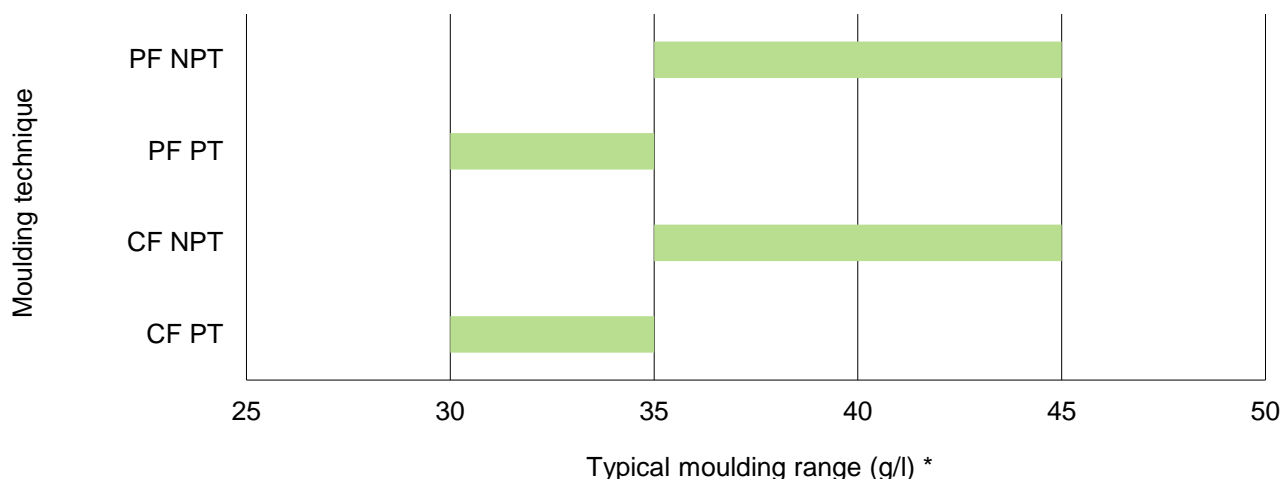

\* Shrinkage, surface aspect and cycle time are influenced by process parameters, tool and equipment layout, and part geometry.

## Pre-treatment

Recommended pre-treatment cycle with pressure tank environment and incoming compressed air both at 23°C:  
5 hours up to 1 bar, decrease and maintain at 0.7 bar throughout production.

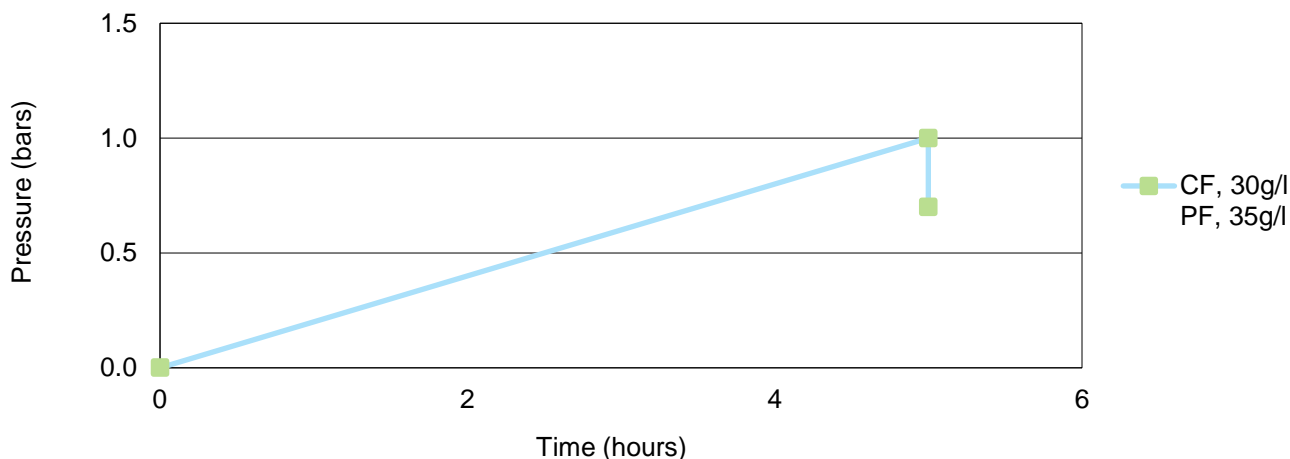

Pre-treatment cycles can be adapted according to moulding process, density and part geometry:

If internal cell pressure is too high, this may lead to fusion issues. In this case, decrease time, pressure or temperature to improve fusion.

Increase time, pressure or temperature to reduce moulded density and improve aspect.

Operating the pressure tank above ambient temperature, up to a maximum of 50°C, significantly shortens pre-treatment time.

## Post-treatment

For moulded densities below 50g/l and depending on the parts dimensions, post-treatment at a temperature of 80°C is recommended for 3 to 8 hours. This helps to remove water content, as well as ensuring dimensional stability and a geometric shape.

## Shrinkage

Typical values range from 2.5% to 3.5%. The higher the moulded density, typically the lower the shrinkage.

## Storage

A storage temperature above 15°C is strongly recommended.

Indoor storage strongly recommended.

If stored outdoors, it is strongly recommended to keep the material indoors for 24 hours before moulding.